

# An Overview of Technologies and Selective Depressing Agents for Separating Chalcopyrite and Talc

Runpeng Liao<sup>1</sup>, Jiushuai Deng<sup>1,2\*</sup>, Hao Lai<sup>1</sup>, Jiaozhong Cai<sup>1</sup>, Xi Zhang<sup>1,2</sup>, Shuming Wen<sup>1</sup>, Hua Yang<sup>3</sup>, Jianying Deng<sup>1</sup>, Jian Fang<sup>1</sup> and Xuesong Sun<sup>1</sup>

<sup>1</sup>State Key Laboratory of Complex Nonferrous Metal Resources Clean Utilization, Kunming University of Science and Technology, Kunming, China

<sup>2</sup>School of Chemical Engineering and Technology, China University of Mining and Technology (Beijing), Beijing, China

<sup>3</sup>Tibet Huatailong Mining Development Co.,Ltd, China Gold, Lhasa 850200, China

## Abstract

Copper-bearing ore containing talc is generally considered as the most refractory type in various chalcopyrite ores, which is predominantly due to the fact that it includes talc and good natural floatability of talc adversely affects the recovery of chalcopyrite. Flotation is the most economical and effective method to separate copper sulfide minerals and talc. For flotation process, there are selective flotation of talc before flotation of copper-bearing minerals, the flotation of copper-bearing minerals with depression of talc, and the bulk flotation of talc and copper-bearing minerals. At present, the researches focus on the depression of talc. The present work reviewed the molecular structure, properties and mechanism of organic and inorganic depressors for talc. The mechanism of action of depressors for talc includes electrostatic interaction, hydrogen bonding and chemical bonding. At the same time, factors such as pH and ionic strength have an important influence on depression effect for talc. The synergism of combined depressors has various novel depression effects on talc surface, which is more efficient than single agent. In the future, separation technology for talc and chalcopyrite develops toward the application of new depressors and the modification of agents. Meanwhile, the development of new depressors for talc needs to consider the properties of associated minerals with talc and copper-bearing minerals. The combined depressors should be developed to maximize the recovery of valuable metals.

## Publication History:

Received: November 16, 2018

Accepted: December 14, 2018

Published: December 16, 2018

## Keywords:

Chalcopyrite, Talc, Separation, Depressor, Depression mechanism

## Introduction

Copper-bearing ore containing talc is regarded as the most refractory type in various chalcopyrite ores, which is predominantly due to the fact that it includes talc [1,2]. Talc is a gangue mineral in many base metal ores including sulfide ores [3]. Talc is a non-polar layered silicate mineral that is hydrophobic, so it is easily floatable [3]. Chalcopyrite is one of the sulfide minerals with good floatability [4-6]. When copper-bearing ores contain more talc, it is difficult to separate chalcopyrite and talc by conventional collectors such as xanthates, resulting in a low grade of copper concentrate. The low-grade copper concentrate causes heavy load in the ore transportation and smelting. In addition, Friedrich Mohs focused on selecting the minerals with his scale-talc, gypsum, calcite, fluorite, apatite, orthoclase, quartz, topaz, corundum, and diamond, where Mohs' hardness scale of talc is 1 [7,8]. That is to say, talc is the world's lowest-hardness ore. Therefore, chalcopyrite ore containing talc will be over crushed and over grinded, resulting in argillization to affect the flotation response [9]. The fine size talc adheres to the bubble surface, leading to sticky flotation bubbles, poor fluidity and poor selectivity. It adversely affects the subsequent flotation of copper-bearing minerals and the copper grade of concentrate. Talc not only deteriorates the flotation conditions, but also increases the consumption of flotation agents [1]. Therefore, it is necessary to develop novel separation processes easy to industrialize for copper-bearing sulfide minerals and talc.

Figure 1 (a) and (c) show the common talc natural crystal and structure model, respectively. Talc  $[Mg_3(Si_2O_5)_2(OH)_2]$  has a T-O-T (2:1 structure), including an octahedral brucite O-layer sandwiched between 2 silica T-layers [3]. Weak van der Waals forces are used to connect T-O-T-layers [3,10]. Through breaking talc particles, it forms two different types of surfaces-the basal plane (or face), and the edge [11]. The basal plane results from the cleavage of the weak bonding between silica layers, regarded to be electrostatically uncharged in aqueous solutions [11]. The subject showed that the negative charge

can be imparted to the basal plane of talc by low levels of substituting SilyAl and Ti [12,13]. The basal planes are hydrophobic due to the low level of substitution and weak bonds exposed to the surrounding water. Wettability studies on the basal planes of talc reported contact angle values were in the range of 60-90° [14,15]. Besides, the edge forms from the rupture of strong ionic and covalent bonds of the silica and brucite layers [11]. Actually, the edges, electrostatically charged with high polarity, are hydrophilic [16,17]. Many researchers have used the density functional theory (DFT) to study properties of talc crystals such as geometric and electronic structure [18-25]. In the tetragonal group (space group  $I42d$ ), chalcopyrite crystallizes with four formulas ( $CuFeS_2$ ) per unit cell [26]. Figure 1(b) and (d) show the natural crystal and structural model of the most common chalcopyrite. The lattice parameters were  $a=b=5.289 \text{ \AA}$  and  $c=10.423 \text{ \AA}$ ; the Fe-S and Cu-S bond lengths were 2.257 and 2.302  $\text{\AA}$ , respectively [26]. In the solid structure, the oxidation number of iron, copper, and sulfur is +3, +1, and -2, respectively [26]. At 0 K, chalcopyrite is assumed to be an anti ferromagnetic material with alternate planes of iron with spin up or down along the  $c$  direction [27]. Some previous researchers carried out DFT calculations on the chalcopyrite's bulk and surface structure to achieve geometric structures in good agreement with experiments [27-35]. They also studied the geometric and electronic properties of chalcopyrite [27-33]. In a word, although talc and chalcopyrite

**Corresponding Author:** Prof. Jiushuai Deng, State Key Laboratory of Complex Nonferrous Metal Resources Clean Utilization, Faculty of Land Resource Engineering, Kunming University of Science and Technology, Kunming 650093, China; E-mail: dengshuai689@163.com

**Citation:** Liao R, Deng J, Lai H, Cai J, Zhang X, et al. (2018) An Overview of Technologies and Selective Depressing Agents for Separating Chalcopyrite and Talc. Int J Metall Mater Eng 4: 146. doi: <https://doi.org/10.15344/2455-2372/2018/146>

**Copyright:** © 2018 Liao et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

have good floatability, their crystal structures are different, which provides the possibility of using selective depressors for their flotation separation.

With more and more attention being given to copper mineral recovery, a review of separation technology and selective depressing agent literature is proposed based on some recent findings. This work attempts to provide an explanation for the current state and use of selective depressing agent. It is expected that this knowledge will expedite the development of efficient, industriable, operable separation of chalcopyrite and talc.

### Separation Technologies

The following four methods are used for the separation of copper sulfide minerals and talc [1,6,9]: (1) Gravity concentrating in advance to remove talc and then recovering copper sulfide minerals by flotation; (2) Preferential talc flotation followed by copper sulfide mineral flotation; (3) Adding depressors for talc with the flotation of copper sulfide minerals; (4) Bulk flotation of talc and chalcopyrite. Wherein, removing talc in advance by gravity concentration leads to reduced copper recovery, thus it is rarely used.

Process for depressing talc with flotation of copper minerals [1,9]: Efficient depressor for talc is used, and then collector is added for the flotation of chalcopyrite. However, some talc can easily enter the concentrate by foam entrainment, resulting in a decrease in chalcopyrite grade.

Bulk flotation of talc and chalcopyrite [1,9]: Bulk flotation refers to the flotation of talc and chalcopyrite to concentrate without pretreatment, then acid leaching can be used to remove talc from concentrate. This method can cause the circulation of talc during the process and the deterioration of flotation, which increases the complexity of the process.

Preferential flotation of talc before the flotation of chalcopyrite [1]: Using frothing agents with good selectivity to float some parts of talc before the flotation of sulfide minerals can reduce the interference of talc to the chalcopyrite flotation.

### Selective Depressing Agents

In the flotation process, the depressor adsorbs on the mineral surface to form a hydrophilic film to prevent the collector from interacting with non-target minerals [36]. According to previous studies, the main depressors for talc can be classified into several categories (Table 1).

Classification	Agent name
Organic compounds	Carboxymethylcellulose [9,37-39]
	Chitosan [40,41]
	Guar gum [9,11,42-45]
	Locust bean gum [40,41]
	Gum arabic [46]
	Sesbania gum [47]
	Tragacanth gum [48]
	Galactomannan [49]
	Lignosulfonate [50-53]
	Dextrin and modified starch [54,55]
Inorganic salts	Combination of ZnSO <sub>4</sub> and Na <sub>2</sub> CO <sub>3</sub> [56]
	Metal salts containing Al <sup>3+</sup> , Cr <sup>3+</sup> , Mg <sup>2+</sup> , Ca <sup>2+</sup> , etc. [10,51,55]
	Water glass, sodium hexametaphosphate, etc. [57,58]

Table 1: Depressors for talc.

### Carboxymethyl cellulose (CMC)

#### Molecular structure and properties of CMC

CMC Carboxymethyl cellulose is a cellulose derivative whose skeleton consists of glucopyranose polymer, often used as the sodium salt (Figure 2) [39]. Some of its hydroxyls are substituted by carboxymethyl groups [39]. CMC's degree of substitution, DS, is one of the most important features. It affects the CMC molecule solubility as well as the solution characteristics [59]. The free acid strength of CMC is similar to that of acetic acid, with the ionization constant of  $5 \times 10^{-5}$ . Therefore, the form of carboxyl in CMC is related to the pH value, and exists in the form of -COO<sup>-</sup> under alkaline conditions and -COOH under acidic conditions [37].

#### Depression mechanism of CMC on talc

The research on adsorption of CMC on talc in the pH range of 2-11 showed the CMC can decrease negative zeta potential of talc with a shift of the IEP from pH 2.5 to 3.5 [60,61]. Moreover, the adsorption of CMC on talc was affected by changes of pH and ionic strength.

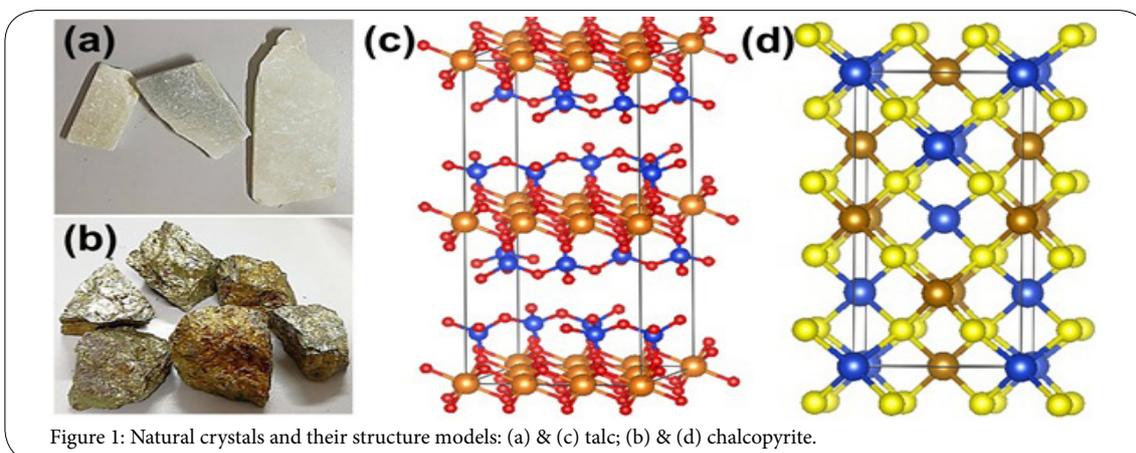


Figure 1: Natural crystals and their structure models: (a) & (c) talc; (b) & (d) chalcopyrite.

These results show the electrostatic force plays an important role in the adsorption of CMC on talc. In general, the main driving forces for CMC adsorption on talc consist of electrostatic interaction and hydrogen bonding instead of hydrophobic force [60].

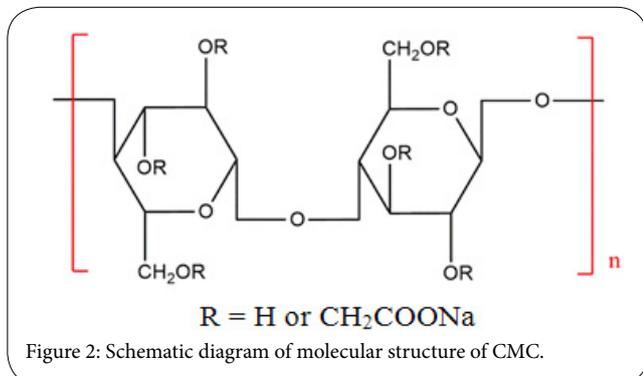


Figure 2: Schematic diagram of molecular structure of CMC.

Wang and Somasundaran [60] found that it is significant for the changes in the infrared bands in the region of  $1000-1080 \text{ cm}^{-1}$ , with the C-O stretch coupled to the C-C stretch and O-H deformation through infrared spectrum comparison before and after reaction of CMC and talc. So it supports strong hydrogen bonding of polysaccharides on the solid [38]. After CMC was adsorbed on talc,  $1632 \text{ cm}^{-1}$  and  $1439 \text{ cm}^{-1}$  absorption peaks were detected and the Mg-O bending vibration peak of  $534 \text{ cm}^{-1}$  in the original talc sample moved to  $501 \text{ cm}^{-1}$ . It indicated -COO- in CMC chain has chemical reaction with talc surface. Luo et al. [38] pointed out that the adsorption of CMC to talc includes electrostatic force, hydrogen bonding and chemical bonding.

In addition, as one of the most widely used talc depressors, CMC has been studied as follows: the effects of solution pH and ionic strength on CMC depression or adsorption control [59,62], the effects of metal ions on CMC depressing talc [63-65], the effects of CMC substitution degree and molecular weight on its depression to talc [59,66-68].

## Chitosan

### Molecular structure and properties of chitosan

Chitosan, with hydroxyl groups and amino groups, is a natural cationic polysaccharide, which is one of the most abundant organic materials in nature [40,69-71]. It is a polysaccharide from the deacetylation of chitin. Figure 3 shows the schematic diagram of molecular structure of chitosan. The pKa value is 6.5 for the amino group of chitosan. In acidic pH range, chitosan is positively charged with the protonation of the amino group. It makes chitosan water-soluble, binding to negatively charged surfaces. However, as the pH increases above neutral, chitosan loses its charge, becoming sparingly soluble in water [72,73].

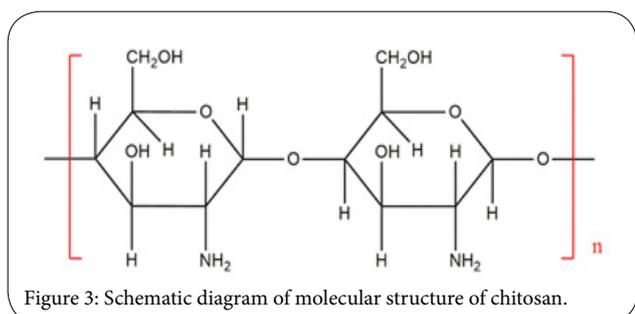


Figure 3: Schematic diagram of molecular structure of chitosan.

### Depression mechanism of chitosan on talc

The depression of an adsorbed chitosan layer on flotation of talc is affected by a change of the solution PH [40,41]. With the chitosan positively charged at pH 3, its adsorption changed the zeta potential of talc from negative to positive [74,75]. However, with the insoluble chitosan on the surface of the talc at pH 9, the adsorption of the non-charged chitosan made the electric double layer slip surface outward. Therefore, it causes the surface potential to zero. The chitosan adsorbed on talc surfaces through physical interactions at pH 3 and 9. The chitosan, positively charged at pH 3, was adsorbed on the talc surface through hydrogen bonding. At pH 9, the chitosan, becoming sparingly soluble in water, deposited on the talc surfaces, leading to the increased adsorbed amount of chitosan [40,41]. It should be noted that chitosan also has a negative impact on chalcopyrite flotation [76].

### Gums-guar gum, locust bean gum, etc

#### Structure, properties and depression mechanism of guar gum

Guar gum, also called as Cyamopsis gum, Guaran, Guyan, Guarina or Glucotard, is a natural non-ionic, water soluble polysaccharide obtained from guar plant [6]. It is a galactomannan consisting of one galactose on every other mannose unit [77]. The ratio of mannose to galactose unit (M/G) is in the range from 1.5:1 to 2:1 because of climate variations [78]. Hydroxyl groups are contained in mannose and galactose-nine are accommodated into each guar monomer unit [42,79]. Figure 4 shows the molecular structure of guar gum.

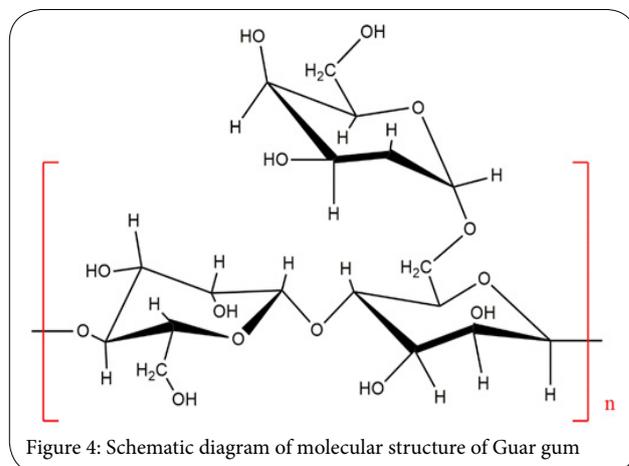


Figure 4: Schematic diagram of molecular structure of Guar gum

Nonionic guar gum gives constant viscosity over the broad pH range. The practical stability is in the range of pH 4 to 10.5. Because of numerous hydroxyl groups across the chain, hydrogen bonding is formed in aqueous solution by guar gum. The basic mannose chain structure of galactomannan, with the single membered galactose branches, increases exposed hydroxyl groups [42].

Electrokinetic studies of adsorption of guar on talc at pH 2-11 showed that guar gum decreased the negative zeta potential of talc rather than reversing it. The changes in pH and the ionic strength level do not affect the adsorption of guar gum on talc. Thus, the electrostatic force is not the main force for the adsorption process. Pyrene fluorescence showed no hydrophobic domain formation for the adsorption of guar gum at talc-aqueous interfaces [43]. The neutral guar gum is adsorbed on the surface of minerals mainly by hydrogen bonding [9,11,44,45].

## Structure and properties of locust bean gum and its depression mechanism

Locust bean gum is a vegetable gum from the seeds of the carob tree. It contains chiefly high-molecular-mass hydrocolloidal polysaccharides, which are composed of galactose and mannose units combined by glycosidic linkages (also described as galactomannan) [40,41,80,81]. Figure 5 shows the molecular structure of locust bean gum.

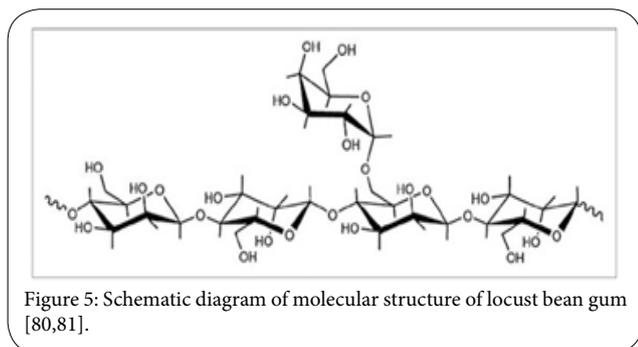


Figure 5: Schematic diagram of molecular structure of locust bean gum [80,81].

Zeta potential measurements were performed on chalcopyrite and talc before and after the addition of locust bean gum. After adding 2000 g/t locust bean gum, the magnitudes of the zeta potentials of both talc and chalcopyrite decreased. That is to say, locust bean gum adsorbed on the surfaces of both minerals. As locust bean gum is non-ionic, the shear plane of the electrical double layer could be stretched by its adsorption on the mineral surface further away from the surface, which lowers the magnitude of the zeta potential. Other studies showed the similar results—the adsorption of non-ionic agents reduced the negative zeta potentials of talc and chalcopyrite, but did not reverse the charges [40,41].

Currently, there are many natural gums with similar properties for depression of talc. Some researchers have tested some related depressors such as gum Arabic [46], sesbania gum [47], tragacanth gum [48] and galactomannan [49]. These depressors, basically similar in their mechanism of action, mainly differ in the pH range of effective depression. In production practice, the economic efficiency and flotation indexes should be considered for the optimal benefits [49,82].

## Lignosulfonate

### Structure and properties of lignosulfonate

Lignosulfonate, a water-soluble lignin extracted from the sulfite pulping process, is a hydrophilic molecule because of its hydrophobic aromatic structure and the presence of the hydrophilic sulfonate groups on its structure [52]. Figure 6 shows the molecular structure of sodium lignosulfonate, whose molecule is approximate to a spherical three-dimensional network structure composed of 50 phenylpropane units [83]. Macromolecule contains hydrophobic backbone (C6–C3 structure moieties linked together by ether and carbon bonds) branched with hydrophilic side chains (carboxyl, sulfonic, and phenolic hydroxyl groups). Therefore, it possesses a certain degree of surface activity as well as remarkable affinity for some metal ions [84]. The pH increased with the increase of the surface charge of lignosulfonate molecules and the aggregation degree of lignosulfonate in solution because of the ionization of sulfonic and phenolic hydroxyl groups [85].

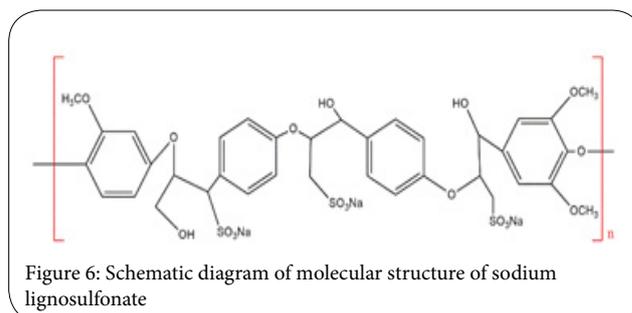


Figure 6: Schematic diagram of molecular structure of sodium lignosulfonate

### Depression mechanism of lignosulfonate

With the increase of surface charge and degree of amnionicity of reagents, the adsorption density of lignosulfonates on talc decreases, showing that electrostatic forces largely control the adsorption process on the net-negatively charged talc surface [50]. Moreover, the infrared spectroscopy analysis showed that sodium lignosulfonate can be chemically adsorbed on the talc surface under strongly alkaline conditions, thus achieving selective depression of talc [51]. The effects of lignosulfonates on the floatability of talc is in alkaline media with various pH values ranging from 7 to 11.2 [52]. Depression of chalcopyrite flotation by lignosulfonates occurs at high pH with lime used for pH control. Therefore, calcium lignosulfonates are stronger depressors compared with sodium salts in lignosulfonate adsorption and mineral depression. However, calcium salts also appear to be less selective [86]. It is different for the adsorption mechanism of each lignosulfonate on the mineral surface. The actual mechanism may be hydrogen bonding, electrostatic interaction, chemical bonding and complexation of calcium ions on the mineral surface [53].

### Al<sup>3+</sup>, Cr<sup>3+</sup>, Fe<sup>3+</sup> and other metal ion depressors

The natural floatability (and zeta potential) of talc, as with other minerals, can be changed substantially through the adsorption of hydroxo complex species of Al<sup>3+</sup>, Cr<sup>3+</sup>, Fe<sup>3+</sup>, etc. [10]. In addition, Ca<sup>2+</sup>, Mg<sup>2+</sup>, Cu<sup>2+</sup>, and Pb<sup>2+</sup> affect the species as well as hydrophilicity or hydrophobicity of talc surface [87,88]. Different metal ions have different effects on the flotation response and potential of talc. When these metal cations are added to the solution, the potential of talc surface changes obviously, indicating the adsorption of several metal ions on the talc surface. The pH values suitable for metal ion depressing talc are related to the favorable pH for metal hydroxide precipitation and the point of zero charge (PZC) of the precipitate [89].

Hydroxyl complexation ions are generated in the corresponding PH range of these above-mentioned metal cations. The adsorption of metal hydroxyl complex ions on talc surface is the main reason for the increase of talc surface potential [90]. There is a strong interaction between water molecules and the surface covered by metal hydroxide precipitation through hydrogen bonds. At the same time, due to the high polarity of metal hydroxide precipitation, the adhesive work of the system is higher than the cohesive work, which further inhibits the hydrophobicity of talc [91]. By using this property, talc can be depressed by adding metal ions in the process of flotation separation of chalcopyrite and talc.

### Dextrin and modified starch

Starch is hydrolyzed to obtain dextrin, a product with low molecular weight and good water solubility. Dextrin is a non-ionic depressor,

used to depress natural hydrophobic minerals. It is more selective than starch.

For adsorption of dextrin (or any polysaccharide) on talc, the most likely mechanism of binding would be through the hydrophobic interaction, involving the hydrocarbon under section of the glucose rings and the hydrophobic face of talc [54].

Carboxymethyl starch is a modified starch etherified with carboxymethyl. Hydroxyl group in the modified carboxymethyl starch forms the chelate with metal cations on the talc surface. The other end of the chelate has a large number of hydroxyl groups that are hydrophilic, thus making talc hydrophilic. At the same time, a large number of hydroxyl groups in carboxymethyl starch molecules can be adsorbed on the talc surface through hydrogen bonding. It enhances the hydrophilicity of talc and decreases its floatability [55].

### Combined depressors

Combined flotation agents are generally more effective than single agent, mainly due to the synergistic effects between agent molecules in the flotation process [92]. According to the literature reports, their main mechanisms of action are composed of the combination mechanism, complexation mechanism, chelation mechanism, co-adsorption mechanism, etc. [36]. Several combined depressors are described below.

### Combined use of $AlCl_3$ and carboxymethyl starch

Firstly,  $AlCl_3$  is added to the ore pulp (with pH 5-6). Then talc surface is electronegative, and aluminum ions and aluminum hydroxide ions are electrostatically adsorbed on the talc surface. The hydroxyl groups in carboxymethyl starch form chelate with aluminum ions and aluminum hydroxide ions adsorbed on the talc surface. The other end of the chelate has a large number of hydroxyl groups that are hydrophilic, which makes talc hydrophilic [55].  $AlCl_3$  and carboxymethyl starch are used as depressors for talc, with low dosage and strong depression effect, while hardly affect the flotation of copper sulfide minerals.

### Combined use of $ZnSO_4$ and $Na_2CO_3$

The effective depressing components of the combined depressor of  $ZnSO_4$  and  $Na_2CO_3$  for talc were solid state  $ZnCO_3$  and  $Zn(OH)_2$ , and  $ZnCO_3$  played a major role. When  $ZnSO_4$  and  $Na_2CO_3$  are used as the combined depressor for talc, the addition of  $Na_2CO_3$  should be strictly controlled at a level suitable for the formation of solid state  $ZnCO_3$ , and the initial concentration of  $ZnSO_4$  should be higher than  $2.5 \times 10^{-4}$  mol/L [56].

### Combined use of $CaCl_2$ and sodium lignosulfonates

The combined action of  $CaCl_2$  and sodium lignosulfonate effectively reduces the content of talc in the chalcopyrite concentrate. The zeta potential measurements, contact angle measurements, and adsorption studies showed that  $Ca^{2+}$  increases the adsorption density of sodium lignosulfonate on the talc surface, with the reduction of the surface potential of talc, and enhancement of the hydrophilicity of talc particles. Thus, it depresses the floatability of talc. These findings were confirmed through XPS analysis. Furthermore, the infrared spectroscopy analysis showed that  $CaCl_2$  and sodium lignosulfonate can be chemically adsorbed on the talc surface in strongly alkaline conditions for selective depression of talc [51].

In addition to the cases mentioned above, there are also many other combined agents such as CMC and sodium hexametaphosphate, and CMC and guar gum. A study indicated that the depression effect of CMC on talc can be facilitated in the presence of  $Ca^{2+}$  and  $CO_3^{2-}$  [93]. Sun [36] developed a combined depressor SY, which is to form a film of poorly soluble compound adsorbed on the talc surface. The combined agents are used to reduce the cost of agents and maximize depression effect, thus maximizing the economic benefits. The main purpose of using combined agents is to reduce the cost of agents and maximize the depression effect of depressors, so as to achieve the maximization of economic benefits.

### Conclusions

Preferential talc flotation followed by chalcopyrite flotation, depression of talc with flotation of chalcopyrite, bulk flotation of talc and chalcopyrite are the main processes for separation of chalcopyrite and talc. To maximize the recovery of chalcopyrite, depression of talc with flotation of chalcopyrite is the most economical and efficient, which has been applied to the copper ore in Dongguashan, the zinc-tin-copper polymetallic ore in Dulong, China, etc.

Depressors for talc are divided into organic compounds and inorganic salts. Carboxymethyl cellulose is one of the most widely used organic depressors, and its adsorption mechanism includes electrostatic force, hydrogen bonding and chemical bonding. Chitosan depresses talc by physical adsorption and hydrogen bond adsorption. It is similar for the mechanism of depressing talc by natural gums such as locust bean gum and arabic gum, mainly controlled by hydrogen bond. The adsorption mechanism of lignosulfonate includes hydrogen bonding, electrostatic interaction, chemical bonding and the complexation of calcium ions on the mineral surface. Dextrin produced by starch hydrolysis is easy to interact with talc. The modified carboxymethyl starch forms chelate and hydrogen bonds with talc to depress the talc flotation. Some metal ions can be adsorbed on the talc surface in the form of hydroxyl complexation ions to form hydrogen bonds.

Combined depressors suggest novel synergistic depression functions, which is more efficient than single agent.

In the future, the separation of chalcopyrite and talc will focus on new depressors and the modification of agents. Meanwhile, the development of new depressors for talc needs to consider the properties of associated minerals with talc and copper-bearing minerals. The combined depressors should be developed to maximize the recovery of valuable metals.

### Funding

This research project has been supported by National Natural Science Foundation of China (Grant No. 51764022, 51464029 & 51404119), Fok Ying Tong Education Foundation (161046), China Postdoctoral Science Foundation (2018M632810) and Open Project of State Key Laboratory of Mineral Processing Science and Technology (BGRIMM-KJSKL-2017-15) and Open Project of Key Laboratory of Biohydrometallurgy, Ministry of Education, Central South University (MOEKL1706).

### Competing Interests

The authors declare that they have no competing interests.

## References

- Shuo-Shi Lu (2010) Research on Crystal Chemistry of Talc and Review and Application of Talc Flotation in Mineral Processing of Nonferrous Sulphide Ores. *Mining & Metallurgy* 24: 517-519.
- Bai L, Liu J, Han Y, Jiang K, Zhao W (2018) Effects of Xanthate on Flotation Kinetics of Chalcopyrite and Talc. *Minerals* 8: 369.
- Farrokhpay S, Ndlovu B, Bradshaw D (2018) Behavior of talc and mica in copper ore flotation. *Applied Clay Science* 160: 270-275.
- Deng JS, Wen SM, Jian L, Wu DD, Feng QC (2014) Adsorption and activation of copper ions on chalcopyrite surfaces: A new viewpoint of self-activation. *Transactions of Nonferrous Metals Society of China* 24: 3955-3963.
- Heyes G, Trahar W (1977) The natural flotability of chalcopyrite. *International Journal of Mineral Processing* 4: 317-344.
- Aghazadeh S, Mousavinezhad SK, Gharabaghi M (2015) Chemical and colloidal aspects of collectorless flotation behavior of sulfide and non-sulfide minerals. *Advances in colloid and interface science* 225: 203-217.
- F Mohs (1825) *Treatise on Mineralogy*. Caledonian Mercury Press, Edinburgh.
- Broz ME, Cook RF, Whitney DL (2006) Microhardness, toughness, and modulus of Mohs scale minerals. *American Mineralogist* 91: 135-142.
- Pan G, Yiping LU (2013) Study on the Inhibition Effect of CMC and Guar Gum in the Talc Flotation. *Nonferrous Metals*.
- Fuerstenau M, Lopez-Valdivieso A, Fuerstenau D (1988) Role of hydrolyzed cations in the natural hydrophobicity of talc. *International Journal of Mineral Processing* 23: 161-170.
- Vidal CG, Pawlik M (2015) Molecular weight effects in interactions of guar gum with talc. *International Journal of Mineral Processing* 138: 38-43.
- Burdukova E, Laskowski J, Bradshaw D (2006) Surface properties of talc and their effect on the behaviour of talc suspensions. *Proceedings of the XXIII International Mineral Processing Congress*. Promed Advertising Istanbul.
- Burdukova E, Becker M, Bradshaw D, Laskowski J (2007) Presence of negative charge on the basal planes of New York talc. *J Colloid Interface Sci* 315: 337-342.
- Fuerstenau D, Huang P (2003) Interfacial phenomena involved in talc flotation and depression. *XXII International Mineral Processing Congress, South Africa*.
- Kaggwa GB, Huynh L, Ralston J, Bremell K (2006) The influence of polymer structure and morphology on talc wettability. *Langmuir* 22: 3221-3227.
- Vidal CG, Pawlik M (2015) Molecular weight effects in interactions of guar gum with talc. *International Journal of Mineral Processing* 138: 8-43.
- Chander S, Wie J, Fuerstenau D (1975) On the native floatability and surface properties of naturally hydrophobic solids. *AIChE Symp Ser*.
- Ulian G, Tosoni S, Valdrè G (2014) The compressional behaviour and the mechanical properties of talc [Mg<sub>3</sub>Si<sub>4</sub>O<sub>10</sub>(OH)<sub>2</sub>]: a density functional theory investigation. *Physics and Chemistry of Minerals* 41: 639-650.
- Larentzos JP, Greathouse JA, Cygan RT (2007) An ab initio and classical molecular dynamics investigation of the structural and vibrational properties of talc and pyrophyllite. *The Journal of Physical Chemistry C* 111: 12752-12759.
- Ulian G, Tosoni S, Valdrè G (2013) Comparison between Gaussian-type Orbitals and Plane Wave ab initio DFT modeling of layered silicates: Talc mineral as model system. *J Chem Phys* 139: 204101.
- Tunega D, Buřko T, Zaoui A (2012) Assessment of ten DFT methods in predicting structures of sheet silicates: Importance of dispersion corrections. *The Journal of Chemical Physics* 137: 114105.
- Bruno M, Prencipe M (2006) Ab initio quantum-mechanical modeling of pyrophyllite [Al<sub>2</sub>Si<sub>4</sub>O<sub>10</sub>(OH)<sub>2</sub>] and talc [Mg<sub>3</sub>Si<sub>4</sub>O<sub>10</sub>(OH)<sub>2</sub>] surfaces. *Physics and chemistry of minerals* 33: 63-71.
- Ulian G, Valdrè G (2015) Density functional investigation of the thermophysical and thermochemical properties of talc [Mg<sub>3</sub>Si<sub>4</sub>O<sub>10</sub>(OH)<sub>2</sub>]. *Physics and Chemistry of Minerals* 42: 151-162.
- Hayashi Y, Akiyama S, Miyaji A, Sekiguchi Y, Sakamoto Y, et al. (2016) Experimental and computational studies of the roles of MgO and Zn in talc for the selective formation of 1, 3-butadiene in the conversion of ethanol. *Physical Chemistry Chemical Physics* 18: 25191-25209.
- Alencar AB, Barboza AP, Archanjo BS, Chacham H, Neves BR (2015) Experimental and theoretical investigations of monolayer and few-layer talc. *2D Materials* 2: 015004.
- Hall S, Stewart J (1973) The crystal structure refinement of chalcopyrite, CuFeS<sub>2</sub>. *Acta Crystallographica Section B* 29: 579-585.
- Oliveira CD, Duarte HA (2010) Disulphide and metal sulphide formation on the reconstructed (0 0 1) surface of chalcopyrite: a DFT study. *Applied Surface Science* 257: 1319-1324.
- Oliveira CD, Lima GF, Abreu HA, Duarte HA (2012) Reconstruction of the Chalcopyrite Surfaces 瑕 A DFT Study. *The Journal of Physical Chemistry C* 116: 6357-6366.
- Wen SM, Deng JS, Xian YJ, Liu D (2013) Theory analysis and vestigial information of surface relaxation of natural chalcopyrite mineral crystal. *Transactions of Nonferrous Metals Society of China* 23: 796-803.
- Oertzen GUV, Harmer S, Skinner WM (2006) XPS and ab initio calculation of surface states of sulfide minerals: pyrite, chalcopyrite and molybdenite. *Molecular Simulation* 32: 1207-1212.
- Li Y, Kawashima N, Li J, Chandra A, Gerson AR (2013) A review of the structure, and fundamental mechanisms and kinetics of the leaching of chalcopyrite. *Advances in colloid and interface science* 197: 1-32.
- Sarvaramini A, Larachi F (2017) Understanding the interactions of thiophosphorus collectors with chalcopyrite through DFT simulation. *Computational Materials Science* 132: 137-145.
- Majuste B, Ciminelli V, Osseo-Asare K, Dantas M, Magalhães-Paniago R, et al. (2012) Electrochemical dissolution of chalcopyrite: Detection of bornite by synchrotron small angle X-ray diffraction and its correlation with the hindered dissolution process. *Hydrometallurgy* 111: 114-123.
- Deng JS, Wen SM, Liu D, Bai SJ, Cao QB, et al. (2013) Internal Geometric and Electronic Structures of Natural Bornite Crystal. in *Applied Mechanics and Materials*. 2013. Trans Tech Publ.
- Deng J, Lei Y, Wen S, Chen Z (2015) Modeling interactions between ethyl xanthate and Cu/Fe ions using DFT/B3LYP approach. *International Journal of Mineral Processing* 140: 43-49.
- Sun Z (2016) Research on copper sulfide flotation and the efficient inhibitor of talc. *Gold*.
- Pan G (2010) Effect of Sodium Carboxymethyl Cellulose on Flotability and Dispersion of Talc. *Metal Mine*.
- Luo C, Zhang X, Su X (2017) Application of CMC Depressant during the Flotation of Copper-Nickel Sulphide Ore in Qinhai. *Nonferrous Metals Engineering* 7: 55-59.
- Krizova H, Wiener J (2013) Development of carboxymethyl cellulose/polyphenols gels for textile applications. *Autex Research Journal* 13: 33-36.
- Feng B, Peng J, Guo W, Zhang W, Ai G, et al. (2018) The effect of changes in pH on the depression of talc by chitosan and the associated mechanisms. *Powder Technology* 325: 58-63.
- Feng B, Peng J, Guo W, Zhu X, Huang W, et al. (2018) The stimulus response of chitosan and its depression effect on talc flotation. *Mineral Processing and Extractive Metallurgy* 127: 56-61.
- Thombare N, Jha U, Mishra S, Siddiqui M (2016) Guar gum as a promising starting material for diverse applications: A review. *Int J Biol Macromol* 88: 361-372.
- Wang J, Somasundaran P, Nagaraj (2005) Adsorption mechanism of guar gum at solid-liquid interfaces. *Minerals Engineering* 18: 77-81.
- Ekmekci BZ, Bradshaw D, Harris P (2007) Adsorption of guar gum and CMC on pyrite. *Minerals engineering* 20: 996-1002.
- Mhlanga S, O'connor C, Mcfadzean B (2012) A study of the relative adsorption of guar onto pure minerals. *Minerals Engineering* 36: 172-178.
- Feng B, Peng J, Zhu X, Luo X (2017) The Role of Acacia in Flotation Separation of Chalcopyrite and Talc. *Acta Mineralogica Sinica* 37: 352-356.
- Zhao K, Gu G, Wang X, Yan W, Hu Y, et al. (2018) The effect of depressant sesbania gum on the flotation of a talc-containing scheelite ore. *Journal of Materials Research and Technology*.
- Wei G, Bo F, Jinxiu P, Wenpu Z, Xianwen Z, et al. (2018) Depressant behavior of tragacanth gum and its role in the flotation separation of chalcopyrite from talc. *Journal of Materials Research and Technology*.
- Zhao K, Gu G, Wang C, Rao X, Wang X, et al. (2015) The effect of a new polysaccharide on the depression of talc and the flotation of a nickel-copper sulfide ore. *Minerals Engineering* 77: 99-106.

50. Ma X, Pawlik M (2007) The effect of lignosulfonates on the floatability of talc. *International Journal of Mineral Processing* 83: 19-27.
51. Fu Y, Zhu Z, Yao J, Han H, Yin W, et al. (2018) Improved depression of talc in chalcopyrite flotation using a novel depressant combination of calcium ions and sodium lignosulfonate. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 558: 88-94.
52. Xu C, Ferdosian F (2017) Utilization of Lignosulfonate as Dispersants or Surfactants. Springer Berlin Heidelberg.
53. Ma X, Pawlik M, Zhang Y, Yu T (2008) The effect of lignosulfonates on the floatability of talc (In Chinese). *Metallic Ore Dressing Abroad* 45: 28-33.
54. Beattie DA, Huynh L, Kaggwa GBA, Ralston J (2006) The effect of polysaccharides and polyacrylamides on the depression of talc and the flotation of sulphide minerals. *Minerals Engineering* 19: 598-608.
55. Chen D, Xue W, Yang J, Dong Y, Li X (2013) A new flotation separation method for copper sulfide minerals and talc.
56. Wang X, Liu R, Ma L, Qin W, Jiao F, et al. (2016) Depression mechanism of the zinc sulfate and sodium carbonate combined inhibitor on talc. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 501: 92-97.
57. Zhang M (2011) Study on synchronous depression of multi mineral phase magnesium silicate minerals in sulfide ore flotation system. Central South University.
58. Lu Y, Zhang M, Feng Q, Ou L, Zhang G, et al. (2012) Sync-suppression Principle of Serpentine and Talc. *Transactions of Nonferrous Metals Society of China* 22: 560-565.
59. Khraisheh M, Holland C, Creany C, Harris P, Parolis L, et al. (2005) Effect of molecular weight and concentration on the adsorption of CMC onto talc at different ionic strengths. *J International Journal of Mineral Processing Parolis* 75: 197-206.
60. Wang J, Somasundaran P (2005) Adsorption and conformation of carboxymethyl cellulose at solid-liquid interfaces using spectroscopic, AFM and allied techniques. *Journal of Colloid and Interface Science* 291: 75-83.
61. Qian G, Bo F, Danping Z, Jujie G (2017) Flotation separation of chalcopyrite from talc using carboxymethyl chitosan as depressant. *Physicochemical Problems of Mineral Processing*. 53: 1255-1263.
62. Morris GE, Fornasiero D, Ralston J (2002) Polymer depressants at the talc-water interface: adsorption isotherm, microflotation and electrokinetic studies. *J International Journal of Mineral Processing Ralston* 67: 211-227.
63. Burdukova E, Leerdam GCV, Prins FE, Smeink RG, Bradshaw DJ, et al. (2008) Effect of calcium ions on the adsorption of CMC onto the basal planes of New York talc - A ToF-SIMS study. *J Minerals Engineering Laskowski* 21: 1020-1025.
64. Cuba-Chiem LT, Huynh L, Ralston J, Beattie DA (2008) In situ particle film ATR-FTIR spectroscopy of carboxymethyl cellulose adsorption on talc: binding mechanism, pH effects, and adsorption kinetics. *Langmuir* 24: 8036-8044.
65. Cuba-Chiem LT, Huynh L, Ralston J, Beattie DA (2008) In situ particle film ATR-FTIR studies of CMC adsorption on talc: The effect of ionic strength and multivalent metal ions. *J Minerals Engineering Beattie* 21: 1013-1019.
66. Gaochan (2010) Effect of Sodium Carboxymethyl Cellulose on Flotability and Dispersion of Talc. *J Metal Mine Pan*.
67. QI C, Ou L, Qiu Z, Li W, Zhang P, et al. (2015) Nonferrous Metals Science and Engineering. Depressing effect of different types of CMC on the surface of two nonpolar minerals. 6: 88-94.
68. Shortridge PG, Harris PJ, Bradshaw DJ, Koopal LK (2000) The effect of chemical composition and molecular weight of polysaccharide depressants on the flotation of talc. *J International Journal of Mineral Processing Schinckel* 59: 215-224.
69. Ravi Kumar MNR (2000) A review of chitin and chitosan applications ☆. *J Reactive and Functional Polymers* 46: 1-27.
70. Knidri HE, Belaabed R, Addaou A, Laajeb A, Lahsini A, et al. (2018) Extraction, chemical modification and characterization of chitin and chitosan. *International Journal of Biological Macromolecules* 120: 1181-1189.
71. Kumar MNR (2000) A review of chitin and chitosan applications. *Reactive and functional polymers* 46: 1-27.
72. Lee DW, Lim C, Israelachvili JN, Hwang DS (2013) Strong adhesion and cohesion of chitosan in aqueous solutions. *Langmuir* 29: 14222-14229.
73. Feng B, Peng J, Guo W, Zhu X, Huang W (2017) The stimulus response of chitosan and its depression effect on talc flotation. *J Mineral Processing and Extractive Metallurgy Imm Transactions* 127: 1-6.
74. Tiraferri A, Maroni P, Rodríguez DC, Borkovec M (2014) Mechanism of chitosan adsorption on silica from aqueous solutions. *Langmuir* 30: 4980-4988.
75. Huang P, Cao M, Liu Q (2011) Using chitosan as a selective depressant in the differential flotation of Cu-Pb sulfides. *International Journal of Mineral Processing* 93: 8-15.
76. Huang P, Cao M, Liu Q (2012) Adsorption of chitosan on chalcopyrite and galena from aqueous suspensions. *Colloids, Surfaces A Physicochemical and Engineering Aspects* 409: 167-175.
77. Yu K, Wong D, Parasrampur J, Friend D, Gum G, et al. (1996) Analytical Profiles of Drug Substances and Excipients. Editor. Academic Press.
78. Gong H, Liu M, Chen J, Han F, Gao C, et al. (2012) Synthesis and characterization of carboxymethyl guar gum and rheological properties of its solutions. *Carbohydrate Polymers* 88: 1015-1022.
79. Jenkins P, Ralston J (1998) The adsorption of a polysaccharide at the talc-aqueous solution interface. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 139: 27-40.
80. Dionisio M, Grenha A (2012) Locust bean gum: exploring its potential for biopharmaceutical applications. *Journal of pharmacy & bioallied sciences* 4: 175.
81. Feng B, Peng J, Zhang W, Ning X, Guo Y, et al. (2018) Use of locust bean gum in flotation separation of chalcopyrite and talc. *Minerals Engineering* 122: 79-83.
82. Zhao KL, Gu GH, Wang H, Wang CL, Wang XH, et al. (2015) Influence of depressant foenum-graecum on the flotation of a sulfide ore which contains hydrophobic gangue. *International Journal of Mineral Processing* 141: 68-76.
83. Yang D, Qiu X, Chen H (2001) *Chemistry Bulletin, The Lignosulfonates for Surfactant* 64: 416-420.
84. Xu L, Mao W, Huang J, Li S, Huang K, et al. (2016) Economical, green route to highly fluorescence intensity carbon materials based on ligninsulfonate/graphene quantum dots composites: Application as excellent fluorescent sensing platform for detection of Fe 3+ ions. *Sensors and Actuators B Chemical* 230: 54-60.
85. Yan M, Yang D, Deng Y, Chen P, Zhou H, et al. (2010) Influence of pH on the behavior of lignosulfonate macromolecules in aqueous solution. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 371: 50-58.
86. Ansari A, Pawlik M (2007) Floatability of chalcopyrite and molybdenite in the presence of lignosulfonates. Part II. Hallimond tube flotation. *Minerals Engineering* 20: 609-616.
87. Yan L, Masliyah JH, Xu Z (2013) Interaction of divalent cations with basal planes and edge surfaces of phyllosilicate minerals: Muscovite and talc. *J Colloid Interface Sci* 404: 183-191.
88. Huang P, Fuerstenau DW (2001) The effect of the adsorption of lead and cadmium ions on the interfacial behavior of quartz and talc. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 177: 147-156.
89. Feng Q, Liu G, Yu Z, Lu Y, Ou L, et al. (2006) Influence and mechanism of ferric and ferrous ions on flotation of talc. *Journal of Central South University* 37: 66-70.
90. Zhang Q, Yuan Z, Liu J, Li L, Lu S, et al. (2016) Influence and Mechanism of Metal Ions on Flotation Behavior of Talc. *Metal Mine*.
91. Liu G, Feng Q, Ou L, Lu Y, Zhang G, et al. (2005) *Journal of The Chinese Ceramic Society*, Influence and mechanism of copper ions and nickel ions on flotation of talc. 33: 1018-1022.
92. Sun Z (2016) Gold, Research on copper sulfide flotation and the efficient inhibitor of talc 37: 54-58.
93. Jin S, Shi Q, Feng Q, Zhang G, Chang Z (2018) The role of calcium and carbonate ions in the separation of pyrite and talc. *Minerals Engineering* 119: 205-211.